



**HAL**  
open science

## **Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> Core-Shell Nanocrystals: Synthesis and Optical Properties**

Benjamin F P Mcvey, Robert A Swain, Delphine Lagarde, Wilfried-Solo Ojo, Kaltoum Bakkouche, Cécile Marcelot, Bénédicte Warot-Fonrose, Yann Tison, Hervé Martinez, Bruno Chaudret, et al.

► **To cite this version:**

Benjamin F P Mcvey, Robert A Swain, Delphine Lagarde, Wilfried-Solo Ojo, Kaltoum Bakkouche, et al.. Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> Core-Shell Nanocrystals: Synthesis and Optical Properties. *Nanomaterials*, 2022, 12, 10.3390/nano12193364 . hal-03836208

**HAL Id: hal-03836208**

**<https://univ-pau.hal.science/hal-03836208>**

Submitted on 1 Nov 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Communication

# Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> Core-Shell Nanocrystals: Synthesis and Optical Properties

Benjamin F. P. McVey<sup>1</sup>, Robert A. Swain<sup>1</sup>, Delphine Lagarde<sup>1</sup>, Wilfried-Solo Ojo<sup>1</sup>, Kaltoum Bakkouche<sup>1,2</sup> , Cécile Marcelot<sup>3</sup> , Bénédicte Warot<sup>3</sup>, Yann Tison<sup>4</sup>, Hervé Martinez<sup>4,5</sup>, Bruno Chaudret<sup>1</sup>, Céline Nayral<sup>1,\*</sup>  and Fabien Delpech<sup>1,\*</sup>

- <sup>1</sup> LPCNO, Université de Toulouse, CNRS, INSA, UPS, 135 Avenue de Rangueil, 31077 Toulouse, France  
<sup>2</sup> Euromed Research Center, Engineering Division, Euro-Med University of Fez (UEMF), Route de Meknes, Rond-Point de Bensouda, Fès 30070, Morocco  
<sup>3</sup> CEMES CNRS UPR 8011 and Université de Toulouse, 29 rue Jeanne Marvig, BP 94347, CEDEX 4, 31055 Toulouse, France  
<sup>4</sup> Université de Pau et des Pays de l'Adour, E2S UPPA, CNRS UMR 5254, IPREM, 64053 Pau, France; Electrochemical Energy Storage Network (RS2E), CNRS FR3459, 33 Rue Saint Leu, CEDEX, 80039 Amiens, France  
<sup>5</sup> Centrale Casablanca, Centre de Recherche Systèmes Complexes et Interaction, Bouskoura 27182, Morocco  
\* Correspondence: cnayral@insa-toulouse.fr (C.N.); fdelpesch@insa-toulouse.fr (F.D.)



**Citation:** McVey, B.F.P.; Swain, R.A.; Lagarde, D.; Ojo, W.-S.; Bakkouche, K.; Marcelot, C.; Warot, B.; Tison, Y.; Martinez, H.; Chaudret, B.; et al. Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> Core-Shell Nanocrystals: Synthesis and Optical Properties. *Nanomaterials* **2022**, *12*, 3364. <https://doi.org/10.3390/nano12193364>

Academic Editors: Sotirios Baskoutas, Zhipeng Sun, Bin Dong and Dong Xie

Received: 21 July 2022

Accepted: 16 September 2022

Published: 27 September 2022

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Copyright:** © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

**Abstract:** II–V semiconductor nanocrystals such as Cd<sub>3</sub>P<sub>2</sub> and Zn<sub>3</sub>P<sub>2</sub> have enormous potential as materials in next-generation optoelectronic devices requiring active optical properties across the visible and infrared range. To date, this potential has been unfulfilled due to their inherent instability with respect to air and moisture. Core-shell system Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> is synthesized and studied from structural (morphology, crystallinity, shell diameter), chemical (composition of core, shell, and ligand sphere), and optical perspectives (absorbance, emission-steady state and time resolved, quantum yield, and air stability). The improvements achieved by coating with Zn<sub>3</sub>P<sub>2</sub> are likely due to its identical crystal structure to Cd<sub>3</sub>P<sub>2</sub> (tetragonal), highlighting the key role crystallographic concerns play in creating cutting edge core-shell NCs.

**Keywords:** nanomaterials; quantum dots; nanocrystal; core-shell nanostructure; cadmium phosphide; zinc phosphide; synthesis; shelling

## 1. Introduction

The size, surface, and composition-dependent optical properties of semiconductor nanocrystals (NCs) give them great potential in range of biomedical (imaging, sensing) and optoelectronic (LEDs, solar cells) applications [1–5]. As synthesized, the optical properties of semiconductor NCs are typically sensitive to ambient conditions (air, moisture), so to truly exploit them in next-generation biomedical and optoelectronic applications, surface passivation reactions are required [1]. The formation of a core-shell semiconductor NC is the most common surface passivation reaction, involving the growth of another material, usually a semiconductor over the NC core. The optical properties of a core-shell NC are highly tunable by considering the electronic properties of the core and shell materials [6–8]. For example, by changing the band alignments of the core and shell, a whole host of optical properties can be altered including absorbance and emission maximum, quantum yield, blinking rates, and an increased resistance to oxidation can be gained [9–12]. There are countless examples of systems, II–VI, IV–VI, and III–V-based nanomaterials where the optical properties have been transformed and exploited thanks to the development of robust core-shell syntheses [10,13,14].

The II–V semiconductors, Zn<sub>3</sub>P<sub>2</sub>, Cd<sub>3</sub>P<sub>2</sub>, Zn<sub>3</sub>As<sub>2</sub>, Cd<sub>3</sub>As<sub>2</sub>, and their alloys represent an emerging class of semiconductor NCs [15–19] with promise in light harvesting and

detection applications. Surface passivation reactions for II–V are underdeveloped compared to the conventional II–VI and IV–VI materials with only a handful of successful reports [20–22].  $\text{Cd}_3\text{P}_2$  absorbs light on a large wavelengths scale with emission across the visible and NIR range (450–1500 nm) with quantum yields of up to 70%, and consequently is an ideal material for light energy conversion, optoelectronic, and telecommunication applications [23–27]. With robust formation protocols [26–30],  $\text{Cd}_3\text{P}_2$  NCs appear as a perfect model to take up the challenges associated to this family and in particular that of growing a shell. Indeed, one of the biggest challenges in utilizing the II–V semiconductors is their extreme sensitivity to air and moisture. To the best of our knowledge, only two examples of coating have been reported for  $\text{Cd}_3\text{P}_2$ . Our group synthesized  $\text{Cd}_3\text{P}_2/\text{ZnS}$  core-shell NCs which showed stable emission 6 weeks post air exposure [26]. However, the shell was thin (0.3 nm), leading to batch dependent air stability. Ding et al. [31] reported the encapsulation of  $\text{Cd}_3\text{P}_2$  NCs within silica nanobeads and polystyrene microspheres. Multiple QDs are contained within the microspheres making their practicality problematic [31]. These strategies having their limits, moving forward there is a great opportunity to study shelling methods for II–V semiconductor nanocrystals.

The purpose of this paper is to investigate the shelling of  $\text{Cd}_3\text{P}_2$  nanocrystals with  $\text{Zn}_3\text{P}_2$  which is an alternate material exhibiting tetragonal structure (this system could be seen as the analog of  $\text{CdSe}/\text{ZnS}$ ). The synthesis and optical properties of core/shell  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs are comprehensively examined from chemical, structural, and optical perspectives. In contrast to the cubic ZnS material previously used,  $\text{Zn}_3\text{P}_2$  leads to a robust type I heterostructure and opens new avenues of fundamental study and  $\text{Cd}_3\text{P}_2$  based applications.

## 2. Materials and Methods

### 2.1. General Synthetic Considerations

All synthetic modifications were carried out in either an argon-filled glovebox with  $\text{O}_2$  and  $\text{H}_2\text{O}$  levels below 0.1 ppm or an argon-filled Schlenk line with a vacuum level between 100 and 150 mTorr. All used glassware was dried in an oven (115 °C) overnight before use. Solvents used, mesitylene, toluene, and pentane, were collected from a puresolv solvent system and degassed with argon for at least 1 h before loading them into the glovebox. Oleylamine was degassed with argon and dried over 4 Å molecular sieves before use.

### 2.2. Synthesis and Purification of $\text{Cd}_3\text{P}_2$ Cores Stabilized with Hexadecylamine

*In situ synthesis of  $\text{Cd}(\text{OAc})_2(\text{HDA})_2$ :* In an argon-filled glovebox 0.1728 g (0.75 mmol) of anhydrous cadmium (II) acetate (99% STREM, Newburyport, MA, USA) is added to a 50 mL Schlenk tube along with either 0.4221 g (1.75 mmol) of hexadecylamine (HDA) (98% Sigma Aldrich, St. Louis, MO, USA). Next, 4 mL of anhydrous toluene (99.9% Honeywell, Charlotte, NC, USA) is added to Schlenk tube, which is then sealed via septa (mixture appears cloudy). The Schlenk tube is then brought out of the glovebox and hooked up to a Schlenk line. The rubber tube connecting the Schlenk tube to the Schlenk line then undergoes 3 cycles of evacuation and purging with argon, before opening the Schlenk tube to the line. The Schlenk tube is then plunged into an oil bath set to 40 °C. The mixture is left to react for 3 h, to insure precursor formation.

*Synthesis of  $\text{Cd}_3\text{P}_2$  NCs:* In an argon-filled glovebox, 0.0671 g (0.25 mmol) of tris(trimethylsilyl) phosphine (98% STREM) is weighed out and dispersed in 1 mL of toluene. **CAUTION: tris(trimethylsilyl) phosphine is pyrophoric, producing toxic byproducts upon exposure to air and moisture.** Tris(trimethylsilyl) phosphine is then withdrawn into a 3 mL syringe and brought out of the glovebox. The syringe containing tris(trimethylsilyl) phosphine is then inserted into the Schlenk tube containing  $\text{Cd}(\text{OAc})_2(\text{HDA})_2$  and is swiftly injected. Immediately upon injection, a color change is observed from cloudy white ( $\text{Cd}(\text{OAc})_2(\text{HDA})_2$ ) to yellow. Over the next 5 min, several more color changes are observed, going from yellow to orange, then red, and finally dark

red. After 2–3 h, the color resembles a dark velvet green. The reaction is then left to react overnight (18 h).

*Purification of Cd<sub>3</sub>P<sub>2</sub> cores stabilized with hexadecylamine:* Unpurified Cd<sub>3</sub>P<sub>2</sub> cores are then transferred into a glovebox and added to a 25 mL Nalgene centrifuge tube (Thermo Fisher) that contains a gas tight rubber O-ring (ensuring an argon atmosphere is maintained during centrifugation). Anhydrous acetonitrile (99.8% Sigma Aldrich) is then added to the unpurified Cd<sub>3</sub>P<sub>2</sub> cores in a 3:1 ratio (i.e., 12 mL of acetonitrile to 4 mL of Cd<sub>3</sub>P<sub>2</sub> cores). The centrifuge tube is then spun at 25,000 RPM for 25 min. After centrifugation, the centrifuge tube is re-entered into the glovebox and the supernatant (light yellow color) is decanted. The centrifuge tube containing Cd<sub>3</sub>P<sub>2</sub> as a pellet is then dried under vacuum on a Schlenk line to remove traces of toluene and acetonitrile. Washed Cd<sub>3</sub>P<sub>2</sub> cores are then dispersed in 5 mL of oleylamine (98% primary amine Sigma Aldrich).

### 2.3. Synthesis and Purification of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> Core-Shell Nanocrystals

*Synthesis of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub>:* 2 mL (0.054 mmol) of purified Cd<sub>3</sub>P<sub>2</sub> cores stabilized with hexadecylamine is added to a 50 mL RB flask. The RB flask is then brought out of the glove box and connected to a Schlenk line. After 3 cycles of evacuation and purging with argon, the RB flask is opened to the line. A temperature probe is then put through one of the RB flasks septa and the reaction heated to 160 °C (ramp rate 25 °C per minute). When the reaction reaches 160 °C, 0.112 g (0.324 mmol) of zinc (II) tris(N,N'-diisopropylacetamidinato) dispersed in 1 mL of oleylamine is added dropwise over a one minute period. After 2 min, 0.0054 g (0.216 mmol) of tris(trimethylsilyl) phosphine (98% STREM) dispersed in 1 mL of oleylamine is added dropwise to the RB flask over a one-minute period. The reaction mixture is then heated to 180 °C and left for 2 h.

*Purification of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub>:* Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> synthesized at low and high temperature is purified in an identical fashion to Cd<sub>3</sub>P<sub>2</sub> cores. The only difference is the purification cycles are repeated twice more with Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub>, i.e., giving a total of 3 purification cycles. Post purification Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> are dispersed in toluene.

### 2.4. Sample Characterization

Low- and high-resolution TEM analysis is performed at the “Centre De Microcaractérisation Raimond Castaing” on a JEOL JEM 1400 electron microscope operating at 120 kV with a point resolution of 4.5 Å and for HRTEM analysis on a JEOL 2100F operating at 200kV with a point resolution of 2.5 Å. Additional high resolution TEM is performed in a Hitachi HF3300 microscope equipped with a Cs corrector. STEM-EDS is performed in a Phillips CM20FEG equipped with a Brücker SDD detector. Samples for TEM analysis are prepared in glovebox by slow evaporation of a drop of the colloidal solution deposited onto a carbon-covered copper grid. The size distributions are determined by measuring at least 250 particles using image J software.

X-ray diffraction spectra are recorded on an MPD Pro Panalytical spectrometer using Co K $\alpha$  radiation with a Kapton film holder. Before sample preparation, a small ring of grease is drawn on the Kapton film. For sample preparation, a highly concentrated solution of nanocrystals dispersed in pentane is drop cast onto Kapton foil within the previously mentioned grease ring. When nanocrystal film is dry, a second piece of Kapton film is placed on top. This second piece becomes stuck to the first piece due to the presence of the grease ring. The sealed Kapton films are then placed in a holder and brought out of the glovebox for XRD analysis.

Solid-state NMR experiments are recorded on a Bruker Avance III 400 spectrometer. Samples are packed into 3.2 mm zirconia rotors inside an argon-filled glovebox. The rotors are spun between 8 to 18 kHz at room temperature. For 1H MAS and 13C DP (direct polarization) MAS experiments, a small flip angle (~30°) is used with recycle delays of 5 s and 10 s, respectively. <sup>31</sup>P Hahn-echo is performed with a recycle delay of 60 s and 6 s, respectively. <sup>13</sup>C CP-MAS and <sup>31</sup>P CP-MAS spectra are recorded with a recycle delay of 2 s

and contact times of 2 ms, 2 ms and 3 ms, respectively. All chemical shifts for  $^1\text{H}$  and  $^{13}\text{C}$  are relative to TMS.  $^{31}\text{P}$  chemical shifts are referenced to an external 85%  $\text{H}_3\text{PO}_4$  sample.

XPS measurements are recorded on a Thermo Electron  $\text{K}\alpha$  spectrometer with a base pressure of  $5 \times 10^{-9}$  mbars. For high-resolution spectra, a pass energy of 20 eV is used and charging effect is neutralized with a dual  $\text{e}^-/\text{Ar}^+$  source. The  $\text{C}1\text{s}$  core peak of adventitious carbon at 285.0 eV is used as an internal energy reference. The data are treated with Casaxps using Gaussian–Lorentzian combinations (GL30) for the fits and Scofield photoionization cross-section [32], corrected for the analysis depth and the analyzer's transmission function, for quantification.

UV–Visible Absorbance spectra are measured by using a Perkin Elmer lambda 35 scanning spectrometer with the sample in a 2 mm cells. Emission spectra are recorded with excitation laser centered at 402 nm (Nichia-NLVH 3000E). The light is then dispersed by a monochromator PI Acton SpectraPro 2500i. The detection is done  $90^\circ$  by CDD camera (Spec-10:100 BR/LN). Acquisition is performed by Winspec32 software.


For determinations of quantum yield (QY), the comparative method outlined by Williams et al. is used. The internal standard used is rhodamine 6G.

For time resolved emission measurements (TR emission) experiments are performed using 1.5 ps laser pulses generated by a tunable mode-locked Ti:Sa laser. A pulse picker is used to reduce the repetition rate from 80 MHz to 0.04 MHz and a second harmonic generation unit converted the excitation wavelength down to 390 nm. The laser beam is focused onto the cuvette on a  $1/e$  diameter spot of  $\sim 100 \mu\text{m}$  and an average power of  $50 \mu\text{W}$ . The PL signal is dispersed by a  $f\#$ -6.5 spectrometer and detected as a function of time by a synchro-scan Hamamatsu streak camera with an overall temporal resolution of 35 ns.


### 3. Results and Discussion

$\text{Cd}_3\text{P}_2$  NCs are prepared using our already published protocol based on  $\text{Cd}(\text{OAc})_2(\text{OcAm})_2$  ( $\text{OcAm}$  = octylamine) and tris(trimethylsilyl) phosphine (PTMS) as reagents [26].  $\text{Cd}_3\text{P}_2$  cores synthesized with octylamine cannot be precipitated via centrifugation so hexadecylamine is substituted for octylamine as the surfactant. Figure S1 shows a TEM image of these synthesized  $\text{Cd}_3\text{P}_2$  cores which are roughly spherical in shape and monodisperse with average size of  $3.6 \pm 0.4 \text{ nm}$  ( $\sigma = 11\%$ ) matching well with previous reports [26].

Our  $\text{Zn}_3\text{P}_2$  shelling protocol (Scheme 1) relies on the use of novel zinc precursor bis-diisopropylacetamidinato zinc(II), referred to as zinc(II) amidinate. This complex is selected for its high reactivity which proved to be highly relevant for the passivation of  $\text{InP}$  QDs and for the synthesis of  $\text{Zn}_3\text{P}_2$  NCs [33]. Briefly, purified  $\text{Cd}_3\text{P}_2$  cores are combined in a round bottom (RB) flask with  $\text{Zn}(\text{amidinate})_2$  and oleylamine as the solvent. The RB flask is then heated to  $180^\circ\text{C}$ , at temperature,  $\text{P}(\text{SiMe}_3)_3$  dissolved in oleylamine is slowly added dropwise. Key to the syntheses' success is the removal of excess Cd precursor from the  $\text{Cd}_3\text{P}_2$  cores, via centrifugation, before shelling. If  $\text{Cd}_3\text{P}_2$  cores are used as synthesized, the excess Cd precursor reacts with  $\text{P}(\text{SiMe}_3)_3$  preferentially, leading to the formation of additional  $\text{Cd}_3\text{P}_2$  NCs. Figure 1a shows a TEM image of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs grown from  $\text{Cd}_3\text{P}_2$  cores stabilized with hexadecylamine. The shape of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs is uniformly spherical in nature, similar to the  $\text{Cd}_3\text{P}_2$  cores. The average size of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs is  $5.7 \pm 0.6 \text{ nm}$  ( $\sigma = 11\%$ ) with a shell width of ca 1.0 nm (Figure 1b). The composition of these shelled NCs is determined using ICP-MS, EDX, and XPS and all these techniques give consistent results close to  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  (Table S1).

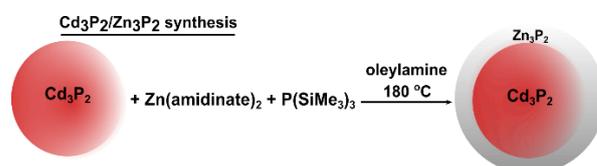

**Scheme 1.** Scheme detailing the synthesis of a  $\text{Zn}_3\text{P}_2$  shell on top of  $\text{Cd}_3\text{P}_2$  cores.

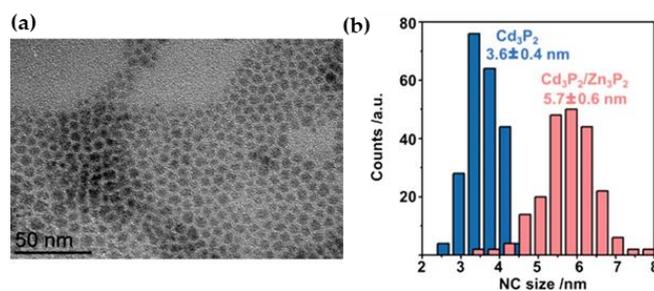

**Figure 1.** (a) TEM image of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> core-shell NCs. (b) Histograms of measured NC sizes for Cd<sub>3</sub>P<sub>2</sub> cores and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> core-shell NCs.

The XRD pattern of Cd<sub>3</sub>P<sub>2</sub> cores and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> are seen in Figure S2. The XRD pattern of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> shows a peak at 50.7° matching the (220) facet of Cd<sub>3</sub>P<sub>2</sub> (cubic or tetragonal structures are not distinguishable at these sizes of crystallites) having shifted towards higher diffraction angles post shelling, consistent with core-shell formation (lattice constraint as usually described) [6]. The XRD peak of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> is also sharper as evidenced by a decrease in the peak FWHM (Table S2) and HRTEM of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> (seen in Figure S2) shows the good crystallinity of the particle.


To examine the coordination sphere of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub>, <sup>1</sup>H-<sup>13</sup>C cross polarization (CP) MAS NMR is used. The CP spectrum of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> shows characteristic peaks at 129.6 and 41.4 ppm matching the carbons double bond and the α-CH<sub>2</sub> resonances of oleylamine, respectively (Figure S3a), demonstrating that the amine is stabilizing the NCs. The P environment of Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> is examined using Hahn-echo <sup>31</sup>P MAS NMR (Figure S3b). This spectrum shows P signal post shelling with one broad peak centralized around −225 ppm and a sharp peak around 6 ppm matching well with metal phosphides and oxidized phosphorus. Integrating the peak area for metal phosphide and oxidized phosphorus gives an oxidation level of 15%. The source of oxidation likely comes from the presence of the acetate ligand in the Cd precursor, similar to previous reports on InP oxidation with In(OAc)<sub>3</sub> precursors [34,35].

XPS analysis is also used to characterize Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> (Figure S4). The presence of Cd, P, and Zn was detected. The P 2p region exhibits 2 doublets. A contribution at low binding energy, 128.1–129.0 eV, is assigned to Cd-P/Zn-P bonding within the nanoparticles [36]. The binding energy of the second doublet, found at 132.8–133.7 eV, is close to the values reported for phosphorus in nitrogen or oxygen environment. Therefore, consistently with the NMR conclusions, this second doublet can be attributed to the phosphate P atoms located at the surface. Regarding cadmium, the Cd 3d doublet is found at 404.9–411.6 eV, which is consistent with a phosphorus environment. The Zn 2p region displays 1 doublet at 1022.0–1045.0 eV which is also in good agreement with Zn-P bonding [37].

Overall, the Zn<sub>3</sub>P<sub>2</sub> shell shows high shape uniformity and the improvement in shell thickness (compared to our previous work on ZnS shelling) is likely due to Cd<sub>3</sub>P<sub>2</sub> and Zn<sub>3</sub>P<sub>2</sub> both having a more favorable lattice mismatch. Due to the small size of crystallites and the low imaging contrast on metal phosphides, XRD and HRTEM on our Cd<sub>3</sub>P<sub>2</sub> samples do not allow to discriminate cubic or tetragonal Cd<sub>3</sub>P<sub>2</sub> structures. However, regarding the easy growth of Zn<sub>3</sub>P<sub>2</sub> (tetragonal structure) shell compared to ZnS (cubic structure) shell on our Cd<sub>3</sub>P<sub>2</sub> cores, it is more likely that they exhibit a tetragonal crystal structure as the shelling material. This is consistent with a previous work of Bawendi which showed the possibility to grow a shell of Cd<sub>3</sub>P<sub>2</sub> on tetragonal Cd<sub>3</sub>As<sub>2</sub> QDs [18]. Interestingly, Cossairt succeeded in growing CdS (cubic structure) tetrapods on cubic Cd<sub>3</sub>P<sub>2</sub> seeds [29]. This is highlighting, once again, the important role that crystallographic matching plays on successful growth of heterostructures, and in our case, in the growth of Zn<sub>3</sub>P<sub>2</sub> shell with high uniformity and robustness.

The optical properties of Cd<sub>3</sub>P<sub>2</sub> and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> are characterized using absorbance and emission (steady state and time resolved) spectroscopies. The absorbance and emission spectra of Cd<sub>3</sub>P<sub>2</sub> cores (blue) and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> (red) core-shell QDs are seen in Figure 2a.

The absorbance spectra of  $\text{Cd}_3\text{P}_2$  cores demonstrates a broad hump from its onset point, 710 nm, with an absorption maximum of 644 nm, matching well with previous reports on this particle size [26]. For  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs, the absorbance spectrum is similarly broad from its onset, 720 nm, with an absorbance maximum of 649 nm. The emission spectra of  $\text{Cd}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs taken at an excitation wavelength of 430 nm are also seen in Figure 2a.  $\text{Cd}_3\text{P}_2$  cores demonstrate an emission maximum of 729 nm with a full width at half maximum (FWHM) of 80 nm, consistently with previous reports [26].  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  core-shells have an emission maximum of 736 nm with a FWHM of 90 nm, giving a 7 nm redshift relative to  $\text{Cd}_3\text{P}_2$  cores. These observations are consistent with previous reports for  $\text{CdSe}/\text{ZnS}$  [10] or the related  $\text{Cd}_3\text{P}_2/\text{ZnS}$  QDs [26] can be assigned to the leakage of the exciton into the shell material.

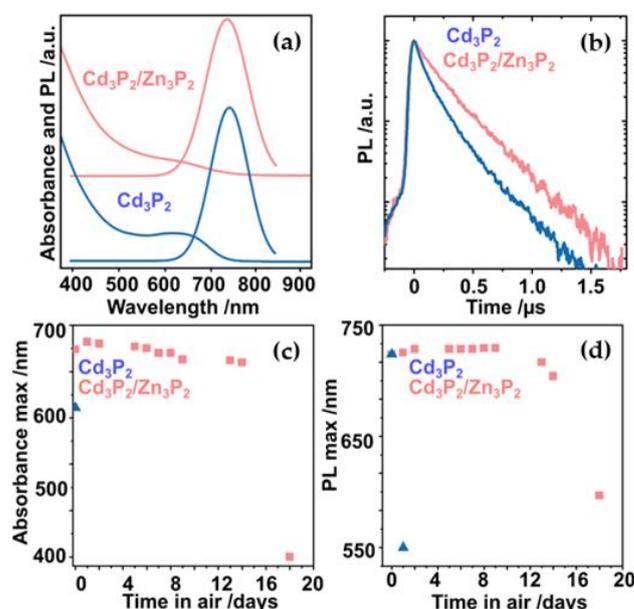

**Figure 2.** (a) Absorbance and emission of  $\text{Cd}_3\text{P}_2$  cores (blue) and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  (red) core-shell NCs sealed in gas tight cuvettes under an Ar atmosphere. (b) Time-resolved emission spectra of  $\text{Cd}_3\text{P}_2$  cores (blue) and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  (red) core-shell NCs (c) and (d) graph showing changes in absorbance and emission maxima of  $\text{Cd}_3\text{P}_2$  (blue triangles) and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  (red squares) NCs upon exposure to air over a 16-day period.

The higher bandgaps of  $\text{Zn}_3\text{P}_2$  (1.5 eV) compared to  $\text{Cd}_3\text{P}_2$  (0.5 eV) should lead to similar absorbance and emission maxima post-shelling due to their type I band alignment [6]. The minor absorbance and emission redshifts (5–10 nm) observed for  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  are consistent with a slight overlap of the exciton into the shell as described by previous reports of type I core-shell QDs ( $\text{CdSe}/\text{ZnS}$ ,  $\text{InP}/\text{ZnSe}$ ) [10,38].

The QYs of  $\text{Cd}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs are calculated by the comparative method using rhodamine 6G as a reference. The QYs of  $\text{Cd}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs are, respectively, 52% and 45%. As this slight difference is within the uncertainty of the comparative method, no significant modification of the QY can be observed post-shelling. This result is reminiscent to our previous work on ZnS coating [26], where the QY of the  $\text{Cd}_3\text{P}_2$  cores (around 50%) is not increased or impacted by the presence of a layer of ZnS.

To gain insight into the fundamental optical properties of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  NCs, time resolved emission spectroscopy is used. All NCs require biexponential fits, with time constants summarized in Table S3. Figure 2b shows the fitted time resolved emission data of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2$  NCs for reference. The two emission components of  $\text{Cd}_3\text{P}_2$  have lifetimes of 110 ns ( $\tau_1$ ) and 290 ns ( $\tau_2$ ) with contributions of 75% and 25%, respectively (average 155 ns). These  $\tau_1$  and  $\tau_2$  values are consistent with an emission from two different types of defects, consistently with previous results for both NCs and bulk

$\text{Cd}_3\text{P}_2$  [30]. After shelling, the two emission components of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  have lifetimes of 140 ns and 290 ns, with contributions of 25% and 75%, respectively (average 253 ns). The difference between the lifetimes before and after shelling is not significant. However, after shelling, the contribution from the first decay component has decreased drastically, 75% to 25%. We assume that the shelling process has led to a partial passivation of the states responsible of the  $\tau_1$  component. The chemical nature of these optically active defects might be related to the surface oxidized phosphorus species,  $\text{PO}_x$ , as seen in the  $^{31}\text{P}$  NMR. Similar observations are seen in the optical properties of  $\text{InP}/\text{ZnX}$  ( $X = \text{S}, \text{Se}$ ) [39], highlighting the detrimental nature oxides can play on NC optical properties. However, compared to well-studied materials such as  $\text{CdSe}$ , the band structure of both  $\text{Cd}_3\text{P}_2$  and  $\text{Zn}_3\text{P}_2$  is not well understood [27,40]. Long-lived emissive transitions in  $\text{Cd}_3\text{P}_2$  QDs have been described in the literature but their cause is still unknown [40]. In our case, the second long-lived transition is not altered by the presence of the  $\text{Zn}_3\text{P}_2$  shell, its origin could be an intraband transition within the  $\text{Cd}_3\text{P}_2$  bandgap, and therefore from an energy perspective, it is unaffected by the higher bandgap  $\text{Zn}_3\text{P}_2$  shell. To fully understand the origin of these emissive transitions, more research is needed.

The stability of  $\text{Cd}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  optical properties with respect to air was monitored using absorbance and emission spectroscopy. Figure 2c,d show respectively the absorbance and the emission maxima of  $\text{Cd}_3\text{P}_2$  and  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  exposed to air over an 18-day period. After 1 day of air exposure, the absorbance and the emission of  $\text{Cd}_3\text{P}_2$  NCs strongly blueshift, demonstrating the high sensitivity of  $\text{Cd}_3\text{P}_2$  cores to air. In contrast, the presence of a  $\text{Zn}_3\text{P}_2$  shell clearly improves the optical stability of  $\text{Cd}_3\text{P}_2$  as reliable QD absorbance and emission remains essentially unchanged for up to 14 days post exposure to air. In comparison, assembly of  $\text{Cd}_3\text{P}_2$  QDs embedded in silica, showed a stability of only 2.5 days in buffer solution [31].

In summary, looking for new directions towards the successful shelling for  $\text{Cd}_3\text{P}_2$  and potentially other II–V materials,  $\text{Zn}_3\text{P}_2$  was explored for the first time as a shelling material. A new synthetic procedure was developed through the use of  $\text{Zn}(\text{amidinate})_2$  and  $\text{P}(\text{SiMe}_3)_3$  as zinc and phosphorus precursors, respectively. Low/high resolution TEM in conjunction with XRD measurements demonstrated that  $\text{Zn}_3\text{P}_2$  shells could be easily grown onto  $\text{Cd}_3\text{P}_2$  cores.  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  core-shell NCs demonstrated nearly identical absorbance/emission maxima and QY compared to  $\text{Cd}_3\text{P}_2$  core. Importantly, the  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  core-shell NCs had significantly higher air stability demonstrating stable QD absorbance and emission up to 14 days post air exposure, compared to  $\text{Cd}_3\text{P}_2$  cores which lost both 1 day post air exposure. This work represents thus a required step towards their practical use in a range of visible/IR based optoelectronic devices.

For the large majority of applications where semiconductors NCs are currently utilized, their true exploitation began after the development of robust shelling materials and strategies.  $\text{Zn}_3\text{P}_2$  exhibiting a tetragonal structure and a bandgap (1.5 eV) higher than the majority of II–V materials, the shelling developed here should be broadly applicable to other II–V tetragonal QDs ( $\text{Cd}_3\text{As}_2$ ,  $\text{Cd}_x\text{Zn}_y\text{As}_2$ ) analogous to shelling common place II–VI and III–V cubic QDs ( $\text{CdSe}$ ,  $\text{CdS}$ ,  $\text{InP}$ ) with  $\text{ZnS}$ . With this synthesis, the next generation of II–V materials can be unlocked for exploration, from fundamental optics to applied materials.

**Supplementary Materials:** The following supporting information can be downloaded at: <https://www.mdpi.com/article/10.3390/nano12193364/s1>, Figure S1: Low (left) and high (right) resolution transmission electron microscopy images of  $\text{Cd}_3\text{P}_2$  cores synthesized with hexadecylamine as the surfactant; Figure S2: High resolution transmission electron microscopy (a) of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  nanocrystals and XRD patterns (b) of  $\text{Cd}_3\text{P}_2$  cores (blue),  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$  (red), the relevant reflections are highlighted for  $\text{Cd}_3\text{P}_2$  00-002-1182 and  $\text{Zn}_3\text{P}_2$  01-002-1264. The \* symbol denotes reflections that are caused by the kapton film; Figure S3: Magic Angle Spinning NMR of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$ : (a)  $^{13}\text{C}$  CP MAS NMR spectra of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$ , (b)  $^{31}\text{P}$  Hahn-echo MAS NMR spectra of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$ ; Figure S4: High resolution XPS of  $\text{Cd}_3\text{P}_2/\text{Zn}_3\text{P}_2$ : (a) P 2p and Zn 3s core peaks; (b) Cd 3d core peaks, the detection of a N 1s peak at ca. 399.0 eV is due to the presence of nitrogen atoms in the oleylamine

ligands; (c) Zn 2p core peaks. The presence of carbon and oxygen is also detected through O 1s and C1 core peaks (not shown here); Table S1: Composition of synthesized nanocrystals from ICP-MS, EDX, and XPS measurements. XPS compositions were determined from the P 2p, Zn 3s and Cd 3d core peaks; Table S2: XRD peak maxima and full width at half maxima for the (220) plan of Cd<sub>3</sub>P<sub>2</sub> and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub>; Table S3: Time-resolved emission measurements: average emission lifetimes of Cd<sub>3</sub>P<sub>2</sub> and Cd<sub>3</sub>P<sub>2</sub>/Zn<sub>3</sub>P<sub>2</sub> core-shell nanocrystals.

**Author Contributions:** B.F.P.M.: investigation, conceptualization, visualization, writing—original draft; R.A.S.: investigation, conceptualization, validation; D.L.: investigation, resources, writing—original draft; W.-S.O.: investigation; K.B.: validation, writing—review & editing; C.M.: investigation, resources, writing—original draft; B.W.: resources, writing—review & editing; Y.T.: investigation, resources, writing—original draft; H.M.: resources, writing—review & editing; B.C.: conceptualization, writing—review & editing; C.N.: supervision, project administration, funding acquisition, writing—original draft, conceptualization, visualization; F.D.: supervision, project administration, funding acquisition, writing—original draft, conceptualization, visualization. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research was funded by the EUR grant NanoX no. ANR-17-EURE-0009 in the framework of the “Programme des Investissements d’Avenir”, the ERC Advanced Grant (MONACAT 2015-694159), the Université Paul Sabatier, the Centre National de Recherche Scientifique (CNRS), the Institut National des Sciences Appliquées (INSA) of Toulouse and the University EuroMed of Fès (UEMF).

**Data Availability Statement:** Not applicable.

**Acknowledgments:** The authors gratefully thank Angélique Gillet, Adeline Pham, and Simon Cayez for technical support.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Boles, M.A.; Ling, D.; Hyeon, T.; Talapin, D.V. The surface science of nanocrystals. *Nat. Mater.* **2016**, *15*, 141. [[CrossRef](#)] [[PubMed](#)]
2. Chen, C.; Corry, B.; Huang, L.; Hildebrandt, N. In Situ Construction of a Cs<sub>2</sub>SnI<sub>6</sub> Perovskite Nanocrystal/SnS<sub>2</sub> Nanosheet Heterojunction with Boosted Interfacial Charge Transfer. *J. Am. Chem. Soc.* **2019**, *141*, 11123. [[CrossRef](#)]
3. Cao, F.; Wang, S.; Wang, F.; Wu, Q.; Zhao, D.; Yang, X. A Layer-by-Layer Growth Strategy for Large-Size InP/ZnSe/ZnS Core-Shell Quantum Dots Enabling High-Efficiency Light-Emitting Diodes. *Chem. Mater.* **2018**, *30*, 8002. [[CrossRef](#)]
4. Wagner, A.M.; Knipe, J.M.; Orive, G.; Peppas, N.A. Quantum dots in biomedical applications. *Acta Biomater.* **2019**, *94*, 44. [[CrossRef](#)] [[PubMed](#)]
5. Litvin, A.P.; Martynenko, I.V.; Purcell-Milton, F.; Baranov, A.V.; Fedorov, A.V.; Gun’ko, Y.K. Colloidal quantum dots for optoelectronics. *J. Mater. Chem. A* **2017**, *5*, 13252–13275. [[CrossRef](#)]
6. Reiss, P.; Protière, M.; Li, L. Core/Shell Semiconductor Nanocrystals. *Small* **2009**, *5*, 154. [[CrossRef](#)]
7. Liu, H.; Hao, J.; Li, J.; Cheng, J.; Gao, Y.; Lin, X.; Wang, K.; He, T. Spectral and Nonlinear Optical Properties of Quasi-Type II CdSe/CdS Nanotadpoles. *J. Phys. Chem. C* **2020**, *124*, 27840. [[CrossRef](#)]
8. Gao, Y.; Qiu, X.; Zhao, F.; Xiao, S.; Li, J.; Lin, X.; Chen, R.; He, T. Linear and nonlinear photophysical properties of ZnSe/CdS/ZnS core/shell/shell type II nanocrystals. *Photonics Res.* **2020**, *8*, 1416. [[CrossRef](#)]
9. Ivanov, S.A.; Piryatinski, A.; Nanda, J.; Tretiak, S.; Zavadil, K.R.; Wallace, W.O.; Werder, D.; Klimov, V.I. Type-II Core/Shell CdS/ZnSe Nanocrystals: Synthesis, Electronic Structures, and Spectroscopic Properties. *J. Am. Chem. Soc.* **2007**, *129*, 11708. [[CrossRef](#)]
10. Hines, M.A.; Guyot-Sionnest, P. Synthesis and characterization of strongly luminescing ZnS-capped CdSe nanocrystals. *J. Phys. Chem.* **1996**, *100*, 468. [[CrossRef](#)]
11. Rabouw, F.T.; Antolinez, F.V.; Brechbühler, R.; Norris, D.J. Microsecond blinking events in the fluorescence of colloidal quantum dots revealed by correlation analysis on preselected photons. *J. Phys. Chem. Lett.* **2019**, *10*, 3732. [[CrossRef](#)] [[PubMed](#)]
12. Chen, O.; Zhao, J.; Chauhan, V.P.; Cui, J.; Wong, C.; Harris, D.K.; Wei, H.; Han, H.-S.; Fukumura, D.; Jain, R.K.; et al. Compact high-quality CdSe-CdS core-shell nanocrystals with narrow emission linewidths and suppressed blinking. *Nat. Mater.* **2013**, *12*, 445. [[CrossRef](#)] [[PubMed](#)]
13. Brumer, M.; Kigel, A.; Amirav, L.; Sashchiuk, A.; Solomesch, O.; Tessler, N.; Lifshitz, E. PbSe/PbS and PbSe/PbSexS1-x Core/Shell Nanocrystals. *Adv. Funct. Mater.* **2005**, *15*, 1111. [[CrossRef](#)]
14. Kim, Y.; Ham, S.; Jang, H.; Min, J.H.; Chung, H.; Lee, J.; Kim, D.; Jang, E. Bright and uniform green light emitting InP/ZnSe/ZnS quantum dots for wide color gamut displays. *ACS Appl. Nano Mater.* **2019**, *2*, 1496. [[CrossRef](#)]
15. Glassy, B.A.; Cossairt, B.M. II<sub>3</sub>V<sub>2</sub> (II: Zn, Cd; V: P, As) Semiconductors: From Bulk Solids to Colloidal Nanocrystals. *Small*. **2017**, *13*, 1702038. [[CrossRef](#)]

16. Glassy, B.A.; Lai, N.L.; Cossairt, B.M. Synthesis of Zn<sub>3</sub>As<sub>2</sub> and (CdyZn1-y)<sub>3</sub>As<sub>2</sub> Colloidal Quantum Dots. *Chem. Mater.* **2017**, *29*, 6195. [[CrossRef](#)]
17. Glassy, B.A.; Cossairt, B.M. Ternary synthesis of colloidal Zn<sub>3</sub>P<sub>2</sub> quantum dots. *Chem. Commun.* **2015**, *51*, 5283. [[CrossRef](#)]
18. Harris, D.K.; Allen, P.M.; Han, H.-S.; Walker, B.J.; Lee, J.; Bawendi, M.G. Synthesis of Cadmium Arsenide Quantum Dots Luminescent in the Infrared. *J. Am. Chem. Soc.* **2011**, *133*, 4676. [[CrossRef](#)]
19. Das, A.; Shamirian, A.; Snee, P.T. Arsenic silylamide: An effective precursor for arsenide semiconductor nanocrystal synthesis. *Chem. Mater.* **2016**, *28*, 4058. [[CrossRef](#)]
20. Lubber, E.J.; Mobarok, M.H.; Buriak, J.M. Solution-Processed Zinc Phosphide ( $\alpha$ -Zn<sub>3</sub>P<sub>2</sub>) Colloidal Semiconducting Nanocrystals for Thin Film Photovoltaic Applications. *ACS Nano.* **2013**, *7*, 8136. [[CrossRef](#)]
21. Miao, S.; Yang, T.; Hickey, S.G.; Lesnyak, V.; Rellinghaus, B.; Xu, J.; Eychmüller, A. Emissive ZnO@Zn<sub>3</sub>P<sub>2</sub> Nanocrystals: Synthesis, Optical, and Optoelectrochemical Properties. *Small.* **2013**, *9*, 3415. [[CrossRef](#)] [[PubMed](#)]
22. Wadia, C.; Alivisatos, A.P.; Kammen, D.M. Materials Availability Expands the Opportunity for Large-Scale Photovoltaics Deployment. *Environ. Sci. Technol.* **2009**, *43*, 2072. [[CrossRef](#)] [[PubMed](#)]
23. Xie, R.; Zhang, J.; Zhao, F.; Yang, W.; Peng, X. Synthesis of Monodisperse, Highly Emissive, and Size-Tunable Cd<sub>3</sub>P<sub>2</sub> Nanocrystals. *Chem. Mater.* **2010**, *22*, 3820. [[CrossRef](#)]
24. Miao, S.; Hickey, S.G.; Rellinghaus, B.; Waurisch, C.; Eychmüller, A. Synthesis and Characterization of Cadmium Phosphide Quantum Dots Emitting in the Visible Red to Near-Infrared. *J. Am. Chem. Soc.* **2010**, *132*, 5613. [[CrossRef](#)] [[PubMed](#)]
25. Miao, S.; Hickey, S.G.; Waurisch, C.; Lesnyak, V.; Otto, T.; Rellinghaus, B.; Eychmüller, A. Synthesis of Monodisperse Cadmium Phosphide Nanoparticles Using ex-Situ Produced Phosphine. *ACS Nano.* **2012**, *6*, 7059. [[CrossRef](#)]
26. Ojo, W.-S.; Xu, S.; Delpech, F.; Nayral, C.; Chaudret, B. Room-Temperature Synthesis of Air-Stable and Size-Tunable Luminescent ZnS-Coated Cd<sub>3</sub>P<sub>2</sub> Nanocrystals with High Quantum Yields. *Angew. Chemie Int. Ed.* **2012**, *51*, 738. [[CrossRef](#)]
27. Cao, H.; Liu, Z.; Zhu, X.; Peng, J.; Hu, L.; Xu, S.; Luo, M.; Ma, W.; Tang, J.; Liu, H. PbS/Cd<sub>3</sub>P<sub>2</sub> quantum heterojunction colloidal quantum dot solar cells. *Nanotechnology.* **2015**, *26*, 035401. [[CrossRef](#)]
28. Mundy, M.E.; Ung, D.; Lai, N.L.; Jahrman, E.P.; Seidler, G.T.; Cossairt, B.M. Aminophosphines as Versatile Precursors for the Synthesis of Metal Phosphide Nanocrystals. *Chem. Mater.* **2018**, *30*, 5373. [[CrossRef](#)]
29. Enright, M.J.; Dou, F.Y.; Wu, S.; Rabe, E.J.; Monahan, M.; Friedfeld, M.R.; Schlenker, C.W.; Cossairt, B.M. Seeded growth of nanoscale semiconductor tetrapods: Generality and the role of cation exchange. *Chem. Mater.* **2020**, *32*, 4774. [[CrossRef](#)]
30. Kornowski, A.; Eichberger, R.; Giersig, M.; Weller, H.; Eychmüller, A. Perspectives on the Physical Chemistry of Semiconductor Nanocrystals. *J. Phys. Chem.* **1996**, *100*, 12467. [[CrossRef](#)]
31. Ding, L.; He, S.; Chen, D.; Huang, M.; Xu, J.; Hickey, S.G.; Eychmüller, A.; Yu, S.-H.; Miao, S. Encapsulated Cd<sub>3</sub>P<sub>2</sub> quantum dots emitting from the visible to the near infrared for bio-labelling applications. *CrystEngComm* **2014**, *16*, 9622. [[CrossRef](#)]
32. Scofield, J.H. Hartree-Slater subshell photoionization cross-sections at 1254 and 1487 eV. *J. Electron Spectrosc. Relat. Phenom.* **1976**, *8*, 129. [[CrossRef](#)]
33. Swain, R.A.; McVey, B.F.P.; Virieux, H.; Ferrari, F.; Tison, Y.; Martinez, H.; Chaudret, B.; Nayral, C.; Delpech, F. Sustainable quantum dot chemistry: Effects of precursor, solvent, and surface chemistry on the synthesis of Zn<sub>3</sub>P<sub>2</sub> nanocrystals. *Chem Commun.* **2020**, *56*, 3321. [[CrossRef](#)] [[PubMed](#)]
34. Cros-Gagneux, A.; Delpech, F.; Nayral, C.; Cornejo, A.; Coppel, Y.; Chaudret, B. Surface chemistry of InP quantum dots: A comprehensive study. *J. Am. Chem. Soc.* **2010**, *132*, 18147. [[CrossRef](#)] [[PubMed](#)]
35. Virieux, H.; le Troedec, M.; Cros-Gagneux, A.; Ojo, W.-S.; Delpech, F.; Nayral, C.; Martinez, H.; Chaudret, B. InP/ZnS nanocrystals: Coupling NMR and XPS for fine surface and interface description. *J. Am. Chem. Soc.* **2012**, *134*, 19701. [[CrossRef](#)]
36. Mobarok, M.H.; Lubber, E.J.; Bernard, G.M.; Peng, L.; Wasylshen, R.E.; Buriak, J.M. Phase-Pure Crystalline Zinc Phosphide Nanoparticles: Synthetic Approaches and Characterization. *Chem. Mater.* **2014**, *26*, 1925. [[CrossRef](#)]
37. Huang, K.; Demadrille, R.; Silly, M.G.; Sirotti, F.; Reiss, P.; Renault, O. Internal Structure of InP/ZnS Nanocrystals Unraveled by High-Resolution Soft X-ray Photoelectron Spectroscopy. *ACS Nano* **2010**, *4*, 4799. [[CrossRef](#)]
38. Dupont, D.; Tessier, M.D.; Smet, P.F.; Hens, Z. Indium Phosphide-Based Quantum Dots with Shell-Enhanced Absorption for Luminescent Down-Conversion. *Adv. Mater.* **2017**, *29*, 1700686. [[CrossRef](#)]
39. Tessier, M.D.; Baquero, E.A.; Dupont, D.; Grigel, V.; Bladt, E.; Bals, S.; Coppel, Y.; Hens, Z.; Nayral, C.; Delpech, F. Interfacial Oxidation and Photoluminescence of InP-Based Core/Shell Quantum Dots. *Chem. Mater.* **2018**, *30*, 6877. [[CrossRef](#)]
40. Wu, K.; Liu, Z.; Zhu, H.; Lian, T. Exciton Annihilation and Dissociation Dynamics in Group II-V Cd<sub>3</sub>P<sub>2</sub> Quantum Dots. *J. Phys. Chem. A* **2013**, *117*, 6362. [[CrossRef](#)]